

A Study on the behaviour of Aluminium alloy (LM13) reinforced with NanoZrO₂ Particulate

Sumod Daniel, Dr .G.Harish

¹Designation: Associate professor ,Department of mechanical engineering. Organisation; Bangalore college of engineering and technology Chandapura,near heelalige railway station, Bangalore-560099 Karnataka.

²Designation: Associate professor ,Department of mechanical engineering. Organisation; University college of engineering . KR circle ,Bangalore-560001. Karnataka.

Abstract: - The present work analyses the characteristic behaviour of the Aluminium alloy (LM13) reinforced with nano-zrO₂ particulates by Stir Casting technique . The experimentation is carried out by distribution nano-zrO₂ particles of size varying from 50-80nm and quantity ranging from 2-10 wt. %.

The composite synthesized is analysed and evaluated in various aspects of strength ,ductility, porosity and hardness by adapting microstructural, mechanical and fractographic techniques and it is arrived that the Nano composite developed has significantly improved strength, hardness, retains residual porosity while compromising slightly with of the resultant composite. The Al – NanoZrO₂ composite thus synthesised displays a significantly reduced Electrical Resistivity and Thermal conductivity.

Keyword: - Al (LM13) metal matrix, Microstructural, Nano-ZrO₂ particulate.stir casting.

I. INTRODUCTION:

With the continued technological advancement in aeronautics, demand for advanced pneumatic components for ultra high end applications is on the rise.[1].Apart from aeronautics, the demand for such materials are also coming from automobiles and electronics sector in which presently used materials such as plastics are likely desired to be replaced by efficient alternates [2].The Al(aluminium) metal matrix alloy structural materials ushered in a revolution in the last decade into the field of automobile engineering by enabling manufacture of light weight body parts and components which significantly reduced fuel consumption in addition to improving the strength of the components and also addressing various concerns on environmental safety and security grounds[3,4].improvising the advantageous abilities of Al matrix alloy by fine tuning the properties of strength and hardness of the alloy is the need of the hour since global demand for high efficiency Al matrix alloy material is rising exponentially[5].comprehensive research into the fabrication of the alloy is being carried out in order to address the shortfalls in it's mechanical properties which imposes an adverse effect in automobile and aeronautical applications and products.[6,7].An exploration into the contemporary research indicates that extensive research is being carried out to overcome the limitations of Al alloy based metal matrix composites(MMC's) such as to overcome the greater coefficient of friction values resulting due to the abrasive act of the dispersoids in the long run thereby significantly increasing the wear on the contact surface.[8-12]. However it is observed that little effort has been made into studying the characteristic behaviour of an Al alloy based MMC reinforced with nanoZrO₂ particulate dispersion.[13]. This research primarily aims to synthesise an Al alloy based composite reinforced with nanoZrO₂ particulates using Stir Casting technique followed by hot extrusion [14]. The composite material developed is studied and analysed in microstructural, mechanical, fractography, thermal and electrical aspects so as to deduce the effect of the nanoZrO₂ particulatesdispersed in standard LM13 Al alloy by increasing the content of Nano particulates added in a step by step manner.

II. EXPERIMENTAL

In this research, the Stir Casting technique is used to disperse the nanoZrO₂ particulates in Al Alloy (LM 13). The chemical composition of the Al alloy involves the following combination of metals (in wt %): Zn - 0.5, Mg - 1.4, Si- 1.2, Ni - 1.5, Fe - 1.0, Mn - 0.5 and Al - bal. The size of the nanoZrO₂ particulates ranges between 50 nm to 80 nm and the quantity added ranges between 2 wt% to 10 wt% with an increase of 2 wt% in every step.The synthesis of NanoZrO₂ reinforced Al composite Containingfive different wt% of nanoZrO₂ reinforcementinvolves producing a melt of the selected matrix material, followed by the introduction of a reinforcing material into the melt, obtaining asuitable dispersion through stirring. This is followed by desired distribution of the reinforcement and subsequent solidification of the melt. To achieve higher particle content in the cast composite the melt temperature is maintained with the partially solid range of the alloy which is called compact processing.This involves heating of the Al alloy in a alumina crucible upto 735°c using resistance furnace and addition of nanoZrO₂ reinforcement which is alreadypre heated to 250°c by constant stirring enabled

by an impeller rotated at 425 rpm so that a vortex is created to get a uniform reinforcement of the nanoZrO₂ particulates in the Al (LM 13) alloy metal matrix. In the second step, the Al (LM 13) metal matrix dispersed with nanoZrO₂ particulates is extruded in a hydraulic press at 255°C. The properties of the nanoZrO₂ reinforcement synthesised is given in table1.

Table 1: Properties of the synthesised nanoZrO₂ reinforcement

Property	Value
Density	8.2 gm/cm ³
MeltingPoint	1860°C
UTS	428 mpa
VHN	151
Young's modulus	97 Gpa

Microstructural characteristics of the polished Al – NMMC specimens are studied using Olympus metallographic microscope. Fractured surfaces of the Al – NMMC are analysed with the help of HITACHI S4100 field emission scanning electron microscope. Vickers micro Hardness measurements are made using Digital Rockwell hardness Tester adopting ASTM E18-94 standard. Tension tests are performed using DutronDigital Tensile Testing machine adopting ASTM E8M-01 standard on AFS standard Tensometer specimens. Fracture toughness Tests are conducted using a closed loop Instron Servo hydraulic material testing system which involves 3 point bend testing of machined specimen precracked by fatigue. Thermal conductivity and electrical resistance are analysed using a comparative method.

III. RESULTS AND DISCUSSION

The integrated Al – nanoZrO₂ metal matrix composite synthesised by employing Stir casting technique and subsequent hot extrusion by hydraulic press yielded better results in terms of retaining the microporosity of the composite, agglomeration and distribution of the nanoZrO₂ particulates over the Al metal matrix thereby producing a sound casting since the technique involves optimum conditions prevailing during the melt, processing, dispersion, deposition and solidification. The resultant NMMC establishes the feasibility of Stir Casting followed hot extrusion technique as a viable, economical and better fabrication technique in the synthesis of nanoZrO₂ metal matrix composite.

3.1. Micro structural Analysis:

Micro structural analysis of the Al - nanoZrO₂ metal matrix composite is performed studying the aspect of distribution of nanoZrO₂ particulates over the base Al alloy metal matrix and integral bonding of the reinforced metal matrix. The analysis revealed the following results:

1. The NMMC cast synthesised, shows uniform distribution of reinforcement with minimal cluster formation of extruded Nano composites thus providing a smoother cast.
2. The cast exhibits better integrated bonding between the nanoZrO₂ reinforcement and Al alloy metal matrix thus yielding a refined grain pattern in the composite thereby minimizing porosity.

The above achievement in the micro structural front is attributed to the Methodology adopted for fabrication of the composite.

Metallographic studies conducted on the samples of NMMC reveals the fact that the reinforcement and the metal matrix have got blended optimally. This optimal integration is because of the capability of the nanoZrO₂ particulates to combine with the Al metal matrix during the process of solidification of the cast with minimal grain growth during recrystallization.

The fractured surface of the end cast of reinforcement and Al Metal matrix is analysed to study the debonding aspects of the nanoZrO₂ particulate- metal matrix interface with the help of a scanning electron microscope HITACHI S4100. The results confirmed of the non-presence of microspores in the contact points of particulate and matrix or any abnormal shrinkage cavity thus it is concluded that the Al - nanoZrO₂ MMC cast is free from any defects in the micro structural front.

3.2. Mechanical Properties:

Table -2: Mechanical Properties of Al-Nano ZrO₂ MetalMatrix Composite

ZrO ₂ (wt%)	Properties			
	HV	0.2% YS(MPa)	UTS(MPa)	Ductility(%)
2	101	124	230	7.4
4	108	132	248	5.8
6	119	158	257	5.0
8	128	183	262	4.2
10	124	171	258	3.5
Matrixalloy(LM13)	90	120	170	11

The mechanical properties of the Al-Nano ZrO₂ MMC were studied to ensure the hardness and strength of the composite and the results are discussed as follows:

- (i) Micro hardness tests conducted on the extruded NMMC samples indicated an increasing rate of hardness with increase in the quantity of Nano ZrO₂ reinforcement and the value peaked at 8wt% (see Table 2).
- (ii) The value of hardness of NMMC peaks at 8wt% at 128 (see Table 2) and then started to decline with further addition of another 2wt% (i.e.) at 10wt% of reinforcement. The increase in hardness of the NMMC under study is primarily attributed to the harder Nano ZrO₂ particulates in the matrix which has solidified and recrystallized with minimum porosity and greater interfacial bonding with better grain refinement.
- (iii) Due to increased grain refinement, there is an increase in the grain boundary area which under applied stress obstructs the dislocation of the composite grain ending up in pile up in the grain boundaries [16]. This in turn increases the strength of the NMMC.
- (iv) The temperature tensile test conducted indicates that the tensile strength of the Al-Nano ZrO₂ MMC has significantly increased which is ascertained from the 0.2% YS and UTS values. This increase in tensile strength is due to effective transfer of applied tensile load to the uniformly distributed well bonded reinforcement [15]. The Nano ZrO₂ particulates with a greater aspect ratio contribute to the building of thermal stress in the reinforcement metal interface resulting due to production of difference in co-efficient of thermal expansion between the two surfaces which also considerably increase the tensile strength.
- (v) The only counterproductive effect of the reinforcement in the Al metal matrix is the ductility of the composite which is because of an induced change of the composites' fracture mode from ductile intergranular to cleavage.

3.3 Fracture toughness

Table – 3

ZrO ₂ (wt.%)	Fracture toughness (Mpa√m)
2	11.5
4	13.8
6	15.1
8	15.5
10	14.0

The Al-Nano ZrO₂ MMC samples are tested for Fracture toughness that Determines the hardness of the composite and in turn stands testimony to the durability of the end cast thus fabricated. The test results concluded that Fracture toughness of the composite increased phenomenally with addition of reinforcement successively and reached peak value of 15.5 Mpa√m for 8wt% addition of reinforcement to the Al alloy and then got reduced for 10 wt% to 14.0 (See table-3). Hence the study establishes the fact that the reinforced composite gains more strength due to the addition of reinforcement since the addition makes Al metal matrix more denser than the monolithic Al alloy (LM13).

A comparative study on fracture surface analysis of FCC structured alloy Samples and the synthesised NMMC samples was conducted to probe the ductility of the two alloys and the results are as follows: In the FCC structured Al alloy the fractured particles of the materials are fine And possess shallow depressions thus making the fracture ductile.

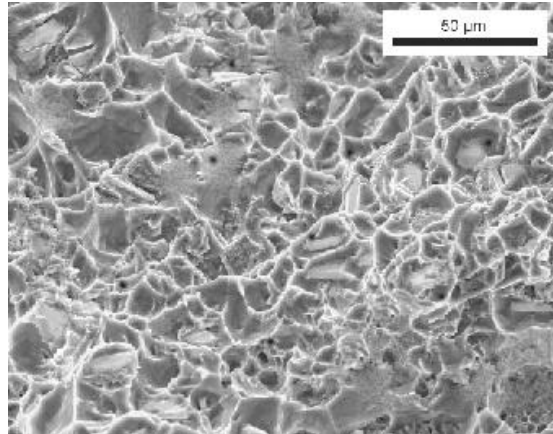


Fig.1. SEM Fractographic image of Al Metal Matrix Alloy (LM13)

However in case of NMMC's (See Fig.2) Containing 8 wt% of reinforcement, the fracture mode is found to be of cleavage type due to excessive distribution of ZrO₂particulates.These particulates under stress are prone to fracture thus reducing the ductility of the composite while on the other hand increasing hardness and strength of the composite considerably.

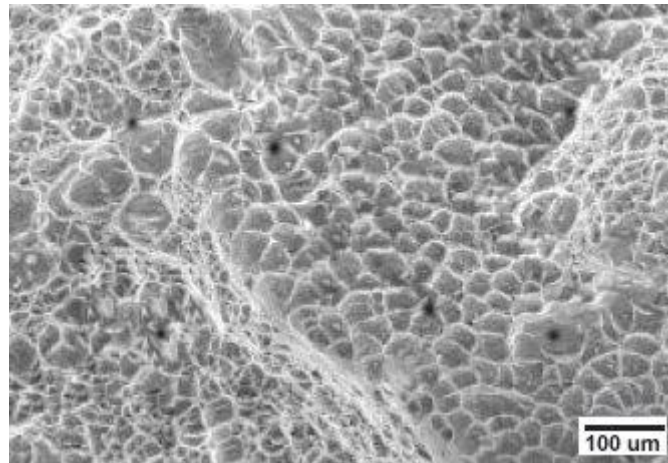


Fig.2. SEM Fractographic image of Al Metal matrix reinforced with 8 wt% of Nano - ZrO₂

3.4 Thermal and Electrical Properties:

Table – 4

Properties		
ZrO ₂ (Wt. %)	Thermal Conductivity (W/mk)	Electrical Resistivity (μΩ-m)
2	140	3.1
4	134	2.8
6	128	2.5
8	120	2.0
10	116	1.8
Al alloy (LM13)	166	3.65

With respect to thermal conductivity,unlike the matrix alloy which has a higher thermal conductivity, the Al Nano ZrO₂MMC synthesised in this work shows reduced thermal conductivity which could be inferred from the table – 4. Thermal conductivity of Al metal matrix significantly decreases with addition of Nano ZrO₂particulates attaining the lowest thermal conductivity for 10 wt% addition of Nano ZrO₂particulates. This reduction is attributed to the fact that increasing ZrO₂particulate content possibly leading to increasing in phonon scattering which reduced thermal conductivity considerably.

In respect of the property of electrical resistivity the NMMC reinforced Al metal exhibits a significantly reducing pattern of electrical resistivity with successive addition of reinforcement of Nano ZrO₂ for the ZrO₂ particulate itself has a lower electrical resistivity within the range between 0.052 to 0.23 $\mu\Omega\cdot m$.

IV. CONCLUSION

The Al Nano-ZrO₂ metal matrix composite synthesised by Stir Casting technique exhibits the following characteristics:

The composite under micro structural analysis displayed a smooth cast with fine grained blending of metal alloy and reinforcement with fair distribution of Nano-ZrO₂ particulates with minimal porosity.

The NMMC exhibits better strength and hardness and improved tensile strength thereby improving the overall mechanical properties of the metal matrix slightly compromising the ductility due to change in the mode of fracture toughness which is revealed from fractographic analysis.

Finally, it is concluded in the part of the electrical and thermal properties that electrical resistivity and thermal conductivity of Al metal matrix is inversely proportional to the addition of reinforcement with Nano-ZrO₂ particulates.

REFERENCES

- [1] M.M. Opeka, I.G. Talmy, J.A. Zaykoki, *J. Mater. Sci.* 32(2004)5887–5894.
- [2] A. Luo, *Metall. Mater. Trans.* 26(1995)2445–2453.
- [3] R.A. Saravanan, M.K. Surappa, *Mater. Sci. Eng. A* 108(2000)276–285.
- [4] S.F. Hassan, J. Gupta, *J. Mater. Sci.* 37(2002)2467–2477.
- [5] S. Awasthi, J.L. Wood, *Adv. Ceram. Mater.* (1988)3449–3458.
- [6] M.O. Lai, *J. Mater. Sci.* 35(2000)2155–2169.
- [7] C.R. Wang, J.M. Yang, *Mater. Chem. Phys.* 74(2002)272–286.
- [8] B. Venkataraman, G. Sundararajan, *Acta Mater.* 44(1996)461.
- [9] S. Murphy, A. Wang, *Mater. Sci. Engg. A* 147 (1991)211
- [10] S. Wilson, A.T. Alpas, *Wear* 212 (1997) 41
- [11] D.P. Mondal, S. Das, R.N. Rao, M. Singh, *Mater. Sci. Eng. A* 402 (2005) 307-319. H. Mifune, *Wear* 213 (1997) 175.
- [12] R. Chen, A. Iwabuchi, T. Shimizu, H. Mifune, *Wear* 213 (1997) 17
- [13] D.J. Lloyd, *Int. Mater. Rev.* 39(1994)1–10.
- [14] Hashim J, Looney L and Hashmi M S J, *Metal Matrix Composites Production by the Stir Casting Method*, Proceeding of the International Conference on Advances in Materials and Processing Technologies, Universidade do Minho, Portugal, July 1997 pp 1-8
- [15] T.S. Srinivasan, M. Gupta, *J. Mater. Eng. Perform.* 8 (1999) 473–489.
- [16] R.E. Reed Hill, *Physical Metallurgy Principles*, 2nd ed., D. Van Nostrand Com-pany, UK, 1964, 56–69.
- [17] C. Garcia, N. Ordas, *J. Nucl. Mater.* 30 (2002) 1282–1294.